

A Failure Analysis of an Experimental AlMgB₁₄ Cutting Tool

J.L. Evans^{*}, L. Deshayes^{**}, D.G. Bhat^{***}, and S.A. Batzer^{*}

^{*} Renfroe Engineering, Inc., Farmington, AR

^{**} National Institute of Standards and Technology, Gaithersburg, MD 20899¹

^{***} Department of Mechanical Engineering, University of Arkansas, Fayetteville, AR 72701

A recently developed ultra-hard boride-based material, AlMgB₁₄, has been fabricated into a standard cutting tool geometry (TPG-222) and tested using single-point turning of Ti-6Al-4V. The initial testing was conducted to compare this new cutting tool's performance relative to a WC-Co cutting tool. During the tests the boride-based inserts suffered catastrophic failure for a wide range of cutting conditions, so a failure analysis was conducted on these inserts.

Ti-6Al-4V is a particularly difficult material to machine due to its mechanical properties but also to its low thermal conductivity and high chemical reactivity. Significant improvements in cutting tool materials must be made for real advancements to occur in machining this alloy [1]. An ultra-hard material based on AlMgB₁₄ is a promising candidate for use in this application [2]. Borides have very low solubility and limited diffusion in titanium, and the AlMgB₁₄ material has a hardness that has been measured to be second only to diamond [3]. Therefore, it is expected that this material will not degrade as quickly as other commonly used cutting tools, such as WC-Co, and is expected to be more economical than cubic Boron Nitride (cBN) materials. The process for fabricating this material was developed at Ames Laboratory, Ames, IA [4]. The process, still in development stages, involves mechanical alloying of elemental powders in a high-energy ball mill and hot pressing the alloyed powders in an inert atmosphere.

Figure 1 shows scanning electron microscope images for two inserts that failed during single-point turning of Ti-6Al-4V using a cutting speed of 30 m/min, a feed rate of 0.25 mm/rev, and a depth of cut of 0.25 mm. The tool inserts have a triangular geometry and the primary mode of failure was nose fracture (see Figure 2). The SEM images in figure 1 reveal excessive porosity on the fracture surface of one of the inserts, suggesting the hot-pressing did not provide full densification. Image B in Figure 1 also shows blocky acicular second-phase particles in the cutting tool material. A crack running through this region shows that the matrix material has pulled away from the second-phase particle. The matrix/particle interface may also lack sufficient strength to provide the tool with adequate mechanical integrity.

Vickers microhardness measurements of this experimental cutting tool material were made using a 1000 gram load and were compared with WC-Co inserts. As expected the hardness was higher in the AlMgB₁₄ material as is indicated by a smaller Vickers indentation (see Figure 3). The measured hardness for the AlMgB₁₄ was HV1000 = 2290 ± 198 (95% C.I.) and the WC-Co hardness was HV1000 = 1812 ± 55 (95% C.I.). But it is observed that the cracks emanating from each corner of the Vickers indent were much longer on the AlMgB₁₄ material than on the WC-Co material. Crack lengths is a qualitative method of evaluating fracture toughness, as is described by Blau and Lawn

¹ Commercial equipment and materials are identified in order to adequately specify certain procedures. In no case does such identification imply recommendation or endorsement by the National Institute of Standards and Technology, nor does it imply that the materials or equipment identified are necessarily the best available for the purpose.

[5]. This test implies that the fracture toughness of the AlMgB_{14} tool material is significantly less than that of the WC-Co material. These results indicate that the toughness of this material needs to be improved.

The processing of this experimental material is still being optimized at the DoE Ames Laboratory. Achieving full density and implementing a new binder phase will substantially increase the fracture toughness; thereby, making this a potentially viable tool material for improved machining of Ti-6Al-4V [6, 7].

References

- [1] X. Yang and R.C. Liu, *Machining Sci. and Tech.* 3 (1) (1999) 107.
- [2] D. G. Bhat, et al., *Machining Sci. and Tech.* 8 (3) (2004) 341.
- [3] B. A. Cook, et al., *Scripta Materialia* 42 (2000) 597.
- [4] B. A. Cook et al. United States Patent No. 6,099,605.
- [5] P. J. Blau, B. R. Lawn, *Microindentation Techniques in Materials Science and Engineering*, ASTM. Intl., Feb. (1986) 303.
- [6] B. A. Cook, et al., *J. of Alloys and Compounds* 366 (2004) 145.
- [7] This work was supported by a subcontract from the DOE. The aid of and helpful comments from Bruce Cook, George Quinn, Brian Lawn, and Rob Ivester are gratefully acknowledged.

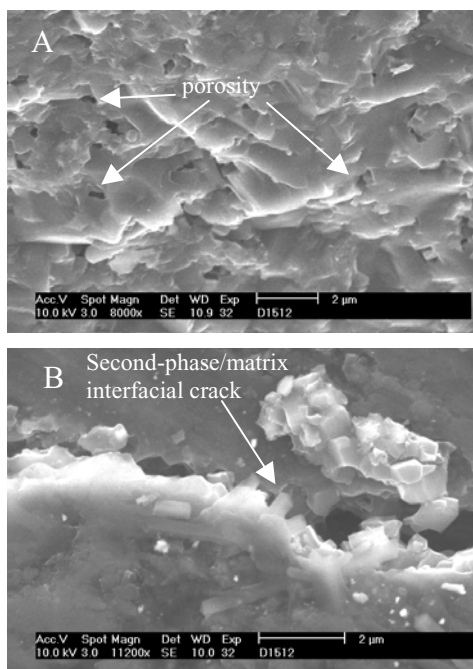


Fig. 1. Scanning electron microscopy images of two fracture surfaces of AlMgB_{14} cutting tools. A. Microporosity is present on the fracture surface. B. The crack interface between the second-phase particle and the matrix material is seen.

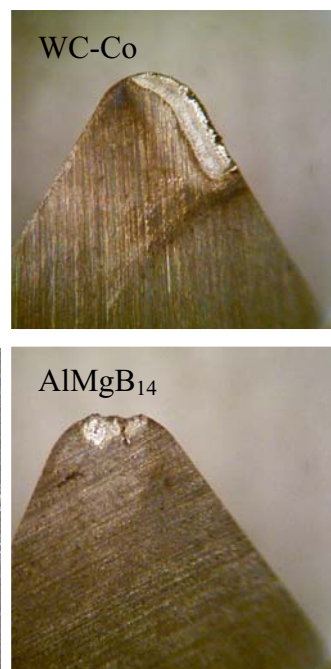


Fig. 2. Optical microscopy images of wear patterns on AlMgB_{14} and WC-Co cutting tools. The AlMgB_{14} presents catastrophic wear (fracture) while WC-Co presents crater wear. Crater wear is an indication of good wear.

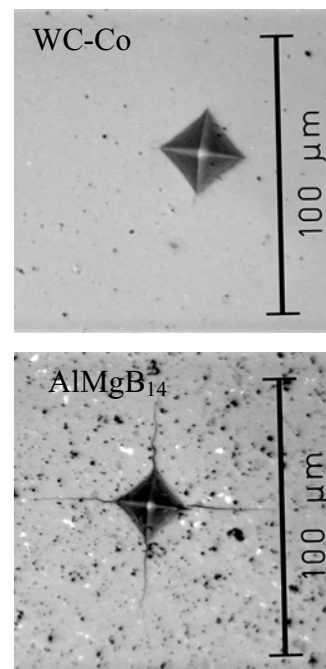


Fig. 3. Optical microscopy images of Vickers microhardness indents on an AlMgB_{14} cutting tool and on a WC-Co cutting tool. The AlMgB_{14} has a higher hardness (smaller indentation), and lower fracture toughness, as indicated by the longer cracks emanating from the corners of the Vickers indents.